



Red Dragon Fruit (*Selenicereus costaricensis*) Waste Peels as Corrosion Inhibitor: Adsorption and Thermodynamic Studies in Acidic Environment

Romulo R. Macadangdang JR*

Department of Medical Technology, Institute of Arts and Sciences, Far Eastern University, Manila, Philippines

Key words: Corrosion inhibition, Red dragon fruit, Green coatings, Adsorption, Thermodynamics.

<http://dx.doi.org/10.12692/ijb/19.3.99-109>

Article published on September 28, 2021

Abstract

Metal corrosion is brought about by the oxidation of atoms on the surface, resulting in irreversible damage to structures at staggering costs. Hence, the search for efficient and cost-effective corrosion inhibitors is relevant. Waste agricultural by-products which have no food or economic value serve as good potential sources for these environmentally benign corrosion inhibitors. Ethanolic extracts of Red Dragon Fruit (RDF) have been previously reported to contain high amounts of flavonoids and polyphenols, which can manifest inhibitory activity against corrosion brought about by aggressive electrolytes. In this study, the ethanolic extract of *Selenicereus costaricensis* waste peels was tested for its anti-corrosion property using weight loss method. We have also probed its performance as a potential corrosion inhibitor at a range of different temperatures from 303 to 343 K. The calculated inhibition efficiency of 2% RDF was 97%. Thermodynamic studies reveal that increasing inhibitor concentration raises the activation parameters of mild steel in an acidic medium such as activation energy (E_a) and changes in enthalpy (ΔH°) and entropy (ΔS°). It was found that the corrosion inhibition process using RDF waste peel extract mainly occurs under diffusion control. Moreover, increased immersion time, inhibitor concentration, and temperature led to increased inhibition efficiency. The spontaneous process ($\Delta G^\circ_{ads} = -23.47$ kJ/mol) of adsorption of RDF on mild steel surfaces obeys the Langmuir isotherm model.

* Corresponding Author: Romulo R. Macadangdang JR ✉ rmacadangdang@feu.edu.ph

Introduction

Corrosion is characterized by the degeneration of surfaces in a particular environment or condition (Sedik *et al.*, 2020). In fact, corrosion imposes a global problem where everyone is concerned because it directly affects the big and small companies and economies of countries. This chemical reaction is a combination of oxidation and reduction processes and has various detrimental effects on infrastructure, resources and art and comes with serious financial implications. Metals, such as mild steel, are of huge value in the industry, whether small-scale or large-scale and in the household. However, when mild steel is exposed to atmospheric oxygen and numerous gases and chemicals, it tends to corrode, which leads to contamination, safety issues and reduction in efficiency (Prashad *et al.*, 2020). The latter is just an example wherein metal, a non-renewable resource, is wasted, which can even lead to the scarcity of metal someday. The need for a low-cost, environment-friendly, and efficient corrosion inhibitor should be addressed.

Since corrosion is a natural phenomenon, metals will just corrode over time, especially if they are left without any maintenance, preventive coatings, or corrosion inhibitors. Several corrosion inhibitors such as novel triazole derivatives (Nahle *et al.*, 2021), Schiff base compounds (Al-Amiry *et al.*, 2021), alkylimidazolium ionic liquids (Hajjaji *et al.*, 2021), and macrocyclic polyether compounds (Paul *et al.*, 2021), plant extracts (Akinbumulo *et al.*, 2020; Deghani *et al.*, 2020; Ogunleye *et al.*, 2020; Hague *et al.*, 2021) have been reported. Among these known corrosion inhibitors, particular interest is pointed to plant extracts as these require facile and green extraction processes.

Selenicereus contaricensis, locally known as red dragon fruit (RDF) has peels characterized by bright red color and no food value (Fig.1). The bright red pigment in RDF was reported to contain rich phytochemicals such as anthocyanins (Rosiana *et al.*, 2021), flavonoids and polyphenols (Padmavathy *et al.*, 2021), which are known antioxidants. In theory,

antioxidants impede the oxidation reaction making this group an excellent choice for corrosion inhibition.

Hence, the goal of this study is to explore the potential of Red Dragon Fruit (RDF) peel ethanolic extract as a corrosion inhibitor for mild steel that was submerged in an acidic medium (1M HCl).

The corrosion inhibition efficiency and corrosion rate were probed by mass loss measurements. A morphological assessment of mild steel products was done using optical microscopy to compare the surface of bare mild steel coupons and their coated counterparts. In addition, this study also aims to elucidate the thermodynamics and adsorption behavior of the adsorption and corrosion inhibition processes.

Materials and methods

Inhibitor preparation, authentication

Selenicereus costaricensis was collected from the Burgos, Ilocos Norte, The Philippines. Voucher specimens were sent to the National Museum of the Philippines for verification and authentication. The extraction protocol was based on a study elsewhere with slight modification (Rosli *et al.*, 2019).

The peels were manually separated, dried, and then pulverized using a blender. Thereafter, 100 g powdered peels were subjected to reflux in 1.0 M HCl solution for the next 4h and kept for an additional 10h. The stock solution (10% v/v) was prepared from the afforded filtrate of the extract. Furthermore, test solutions ranging from 0.05% to 2% v/v concentration were prepared from the stock solution after further dilution with the correct quantity 1.0 M HCl.

Preparation of specimen

Mild steel specimens of size 1.0 x 5.0 x 0.5 cm³ were polished with 400 and 600-grade emery paper, degreased with acetone in a sonic bath, washed with deionized water (Ultrapure Milli-Q), dried and kept in a desiccator for the experimental study.

Mass loss measurements

In separate containers, pre-weighed mild steel samples were suspended in 120 mL of 1.0 M HCl solutions containing different inhibitor concentrations and the controls with the aid of a glass hook at various immersion periods such as 1h, 4h, 7h, and 24h at room temperature (Rosli *et al.*, 2019). The samples were then removed, washed with deionized water, dried, and reweighed after the specified time of immersion.

The inhibition efficiency (IE%) was calculated as a percentage using Equation 1:

$$IE\% = \frac{(W_0 - W_x)}{W_x} 100\% \quad (1)$$

where W_0 is the weight loss (in mg) of metal without RDF inhibitor and W_x is the weight loss (in mg) of metal with RDF inhibitor.^[9]

Further, the rate of corrosion (R_c) was calculated using Equation 2:

$$R_c = \frac{\Delta W}{A t} \quad (2)$$

where ΔW is the change in weight (mg), A is the exposed area (cm^2), and t corresponds to the exposure time (h).^[9]

To explore the thermodynamics of the process, same methodology was applied at elevated temperatures (303K-343K), keeping the immersion time constant at 1h. All measurements were done in triplicates and the values that appear henceforth are the reported means (Kavitha *et al.*, 2019).

Surface examination studies

Surface analysis of mild steel specimens was done to study the changes that occurred during the corrosion of mild steel in the absence and presence of inhibitors. The inhibitive action of plant extracts on mild steel corrosion was investigated by the Optical Microscope technique. The micrographs of the uninhibited and inhibited specimens were obtained,

which aided the examination of the nature of the corrosion product formed on the surface of mild steel samples. The micrographs were compared in terms of the amount of visible amount of corrosion, such as the amount of orange-to-reddish brown streaks and amount of pitting involved.

Statistical analysis

Statistical Package for the Social Sciences (SPSS) 27.0 was used for the data analysis of this study. The data collected were tested using a two-way analysis of variance (ANOVA) as there were two parameters in the study—immersion time and concentration. It was used to determine if there are any significant differences ($\alpha=0.05$) between the different set-ups. In this way, the level of significance was found and determined whether the extract could lessen the rate of corrosion in mild steel.

Results and discussion

Mass loss measurements

Effect of concentration: Owing to the simplicity of method and high reliability, the weight loss method was employed to monitor the corrosion rate of mild steel in an acidic medium in the presence and absence of red dragon fruit peels extract as an inhibitor. Moreover, the mass loss method was also used to estimate the inhibition efficiency of the RDF at varying concentrations. Fig. 2 depicts the relationship of inhibitor concentration (% v/v) with corrosion rate ($\text{mg}/\text{cm}^2\text{h}$) and inhibition efficiency (IE%). With an increase in RDF inhibitor concentration from 1% to 2%, the corrosion rate followed a downward trend while improved inhibition efficiency was observed in 7h and 24h immersion times. Immersion times of 1h and 4h revealed that protection by the RDF coating from acid attack is still premature. This result signals that adsorbed RDF particles onto the surface at 24h immersion time of mild steel specimens served as the optimum time to provide a protecting stratum (Telegdi, 2020; Prabakaran *et al.*, 2016).

Effect of immersion time: At constant temperature, the effect of immersion time from 1h up to 24h was investigated.

Table 1. Effect of immersion time at constant temperature.

RDF Conc (% v/v)	Immersion time (h)							
	1		4		7		24	
	R _c	IE	R _c	IE	R _c	IE	R _c	IE
Blank	18.29		6.30		4.36		3.39	
0.050	17.96	1.79	5.74	8.76	3.91	10.27	2.19	35.55
0.50	17.64	3.54	4.74	24.73	3.49	19.90	1.50	55.87
1.0	17.37	4.99	4.69	25.50	2.82	35.39	1.31	61.51
2.0	13.38	26.83	4.12	34.58	3.25	37.27	0.09	97.41

$T = 300K$ | $R_c = mg\ cm^{-2}h^{-1}$ | $IE = \%$.

Table 1 suggests that increasing immersion time leads to enhanced inhibition efficiency and a lower corrosion rate. The highest value for inhibition efficiency, 97.41%, was charted at 2.0% RDF loading at 24 hours. This suggests that longer immersion time allows the constituents of RDF to fully saturate the surface of mild steel thus, providing an efficient

protective barrier against corrosion. For the adsorption of RDF extracts on mild steel in this study, no significant signs of desorption were detected, contrary to previously reported literature where deterioration of inhibition efficiency was observed (Jyothi *et al.*, 2019).

Table 2. Effect of various temperatures on corrosion rate on mild steel corrosion in acidic environment.

RDF Conc (% v/v)	Temperature (K)				
	303	313	323	333	343
Blank	5.65	7.17	9.48	12.56	20.50
0.050	5.57	7.03	9.13	11.96	15.13
0.50	5.39	6.76	9.24	11.75	15.08
1.0	5.26	6.55	9.01	11.59	14.99
2.0	4.21	5.83	8.57	11.36	13.92

$Immersion\ time = 24h$ | $R_c = mgcm^{-2}h^{-1}$ | $IE = \%$.

Effect of temperature: To probe the thermodynamics and stability of the adsorption process of RDF on mild steel, similar protocols were performed as above, but with temperature variation from 303 K to 343 K at a constant immersion time (24h) as summarized in Table 2. A marked rise in the rate of corrosion was observed with increasing temperature, especially in the unprotected surface of the blank. Meanwhile,

corrosion rate slowed down with higher % RDF extract concentration even at elevated temperatures.

It is apparent that the presence of RDF constituents on the mild steel surface prevented the disbanding of metal from the bulk sample and this may be due to the formation of iron-RDF complex layer via physical sorption (Al Maofaria *et al.*, 2021).

Table 3. Values of activation parameters obtained for MS in 1M HCl solution at various concentration of inhibitor.

	RDF concentration (% v/v)				
	Blank	0.05%	0.50%	1.00%	2.00%
slope	-2619.8	-2626.8	-2711.0	-2767.8	-3187.6
E_a (kJ mol ⁻¹)	21.78	21.84	22.54	23.01	26.50
r^2	0.9961	0.9976	0.9971	0.9900	0.9938

The effect of temperature on corrosion rate as a function of inhibitor concentration is presented in Fig. 3.

Determination of activation and thermodynamic parameters

The mechanism of corrosion inhibition is revealed through the determination of the activation energy by changing the temperature in the presence and absence of inhibitors. Using the Arrhenius equation,

$$R_c = A e^{\left(\frac{-E_a}{RT}\right)} \quad \text{Eq. 3}$$

where R_c is the corrosion rate, E_a is the activation energy, T is the temperature in Kelvin, A is the

Arrhenius pre-exponential constant, and R is the universal gas constant ($8.314 \text{ Jmol}^{-1}\text{K}^{-1}$), a plot of $\ln R_c$ as a function of inverse temperature ($1/T$) allows the estimation of activation energy (Fig. 3). Based on the gathered data, the inhibitor did not change the activation energy process within the experimental error of $25 \pm 3 \text{ KJ/mol}$ (Table 3). This, therefore, signifies that the process mainly occurs under diffusion control (Bayol *et al.*, 2008; Africa, 2008).

Other thermodynamic parameters such as standard enthalpy of activation and standard entropy of activation were also calculated from the results of temperature variation studies using the transition state equation.

Table 4. Standard enthalpy and standard entropy of the adsorption of RDF on mild steel.

	RDF concentration (% v/v)				
	Blank	0.05%	0.50%	1.00%	2.00%
ΔH° (KJmol ⁻¹)	18.73	19.16	19.87	20.33	23.83
ΔS° (Jmol ⁻¹ K ⁻¹)	-180.20	-167.74	-165.68	-164.41	-154.38

Table 5. Equilibrium constant and standard Gibbs energy for RDF adsorption.

Mass loss measurements					
Immersion time	Slope	Y-intercept	r^2	$\ln K_{ads}$	ΔG (kJ mol ⁻¹)
24hr	1.4652	0.1201	0.9984	12.20	-23.47

$T = 300\text{K}$.

$$R_c = \frac{RT}{N_A h} e^{\left(\frac{-\Delta H^\circ}{RT}\right)} e^{\left(\frac{\Delta S^\circ}{R}\right)} \quad \text{Eq. 4}$$

where N_A is Avogadro's number and h is Planck's constant. The slopes and intercepts of the graphs presented in Fig. 4 allowed the calculation of these thermodynamic parameters.

Other thermodynamic parameters are presented in Table 4. The calculated values for the enthalpy of activation ranges from 18.73 to 23.83 kJmol⁻¹ indicating an endothermic and physical adsorption process. Meanwhile, the negative values for the entropy of activation strongly suggest a non-spontaneous phenomenon in the case of adsorption of RDF onto the surface of the mild steel. This suggests

the associative formation of RDF-MS complex hence a decline in disorder (Graham, 1953).



Fig. 1. Red dragon fruit (*S. costaricensis*) peels.

Adsorption Isotherm

Studies on adsorption isotherms were performed to further grasp the interaction of RDF inhibitors and the mild steel substrates. The surface coverage parameter (θ) for different concentrations of RDF was calculated from the weight loss data. Graphical testing was used to find an appropriate adsorption isotherm. A plot of C/θ as a function of concentration was generated to afford the data presented in Fig. 5.

The graphs show linear slopes conforming to the Langmuir model ($r^2 \cong 1$) at immersion times greater than 4h. Moreover, this result confirms that 1hr immersion time was not enough for RDF to saturate the surface of the substrate. Immersing the system in 4h and 7h showed high linearity. However, the 24h immersion time yielded a value closest to unity (0.9984).

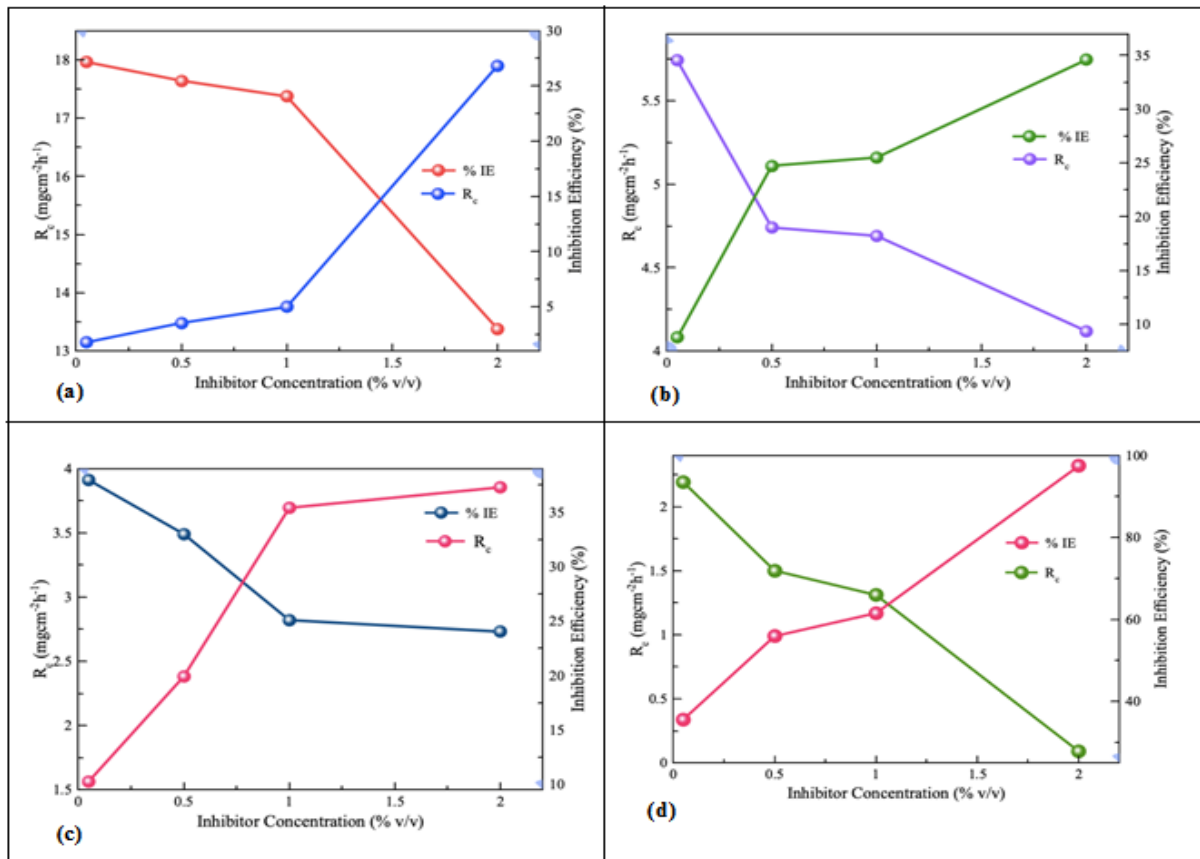


Fig. 2. Corrosion rate and inhibition efficiency as a function of concentration at different immersion times: (a) 1hr (b) 4 hr (c) 7 hr (d) 24 h.

This means that 24h is the most appropriate immersion time allowing RDF constituents to fully adsorb on the exposed surfaces of the mild steel samples.

The standard free energy of adsorption (ΔG_{ads}) calculated using the equation,

$$\Delta G_{ads} = -RT \ln(K_{ads} \cdot xA) \tag{Eq.5}$$

where, R is the gas constant (8.314 Jmol⁻¹K⁻¹), K_{ads} is

the equilibrium constant for adsorption, T is the temperature (300 K) and A is water density. Table 5 summarizes the computed values of the ΔG_{ads} and K_{ads} . For the curves that obey the Langmuir isotherm, the calculated values for the standard free energy ranges from -23.47 to -20.56 kJmol⁻¹ which is typical of physisorptions (Li *et al.*, 2011). Therefore, the adsorption of RDF extract on the surface of mild steel did not involve electron sharing to afford a chemical bond (El Hamdani *et al.*, 2021; Krishnaveni & Ravichandran, 2014).

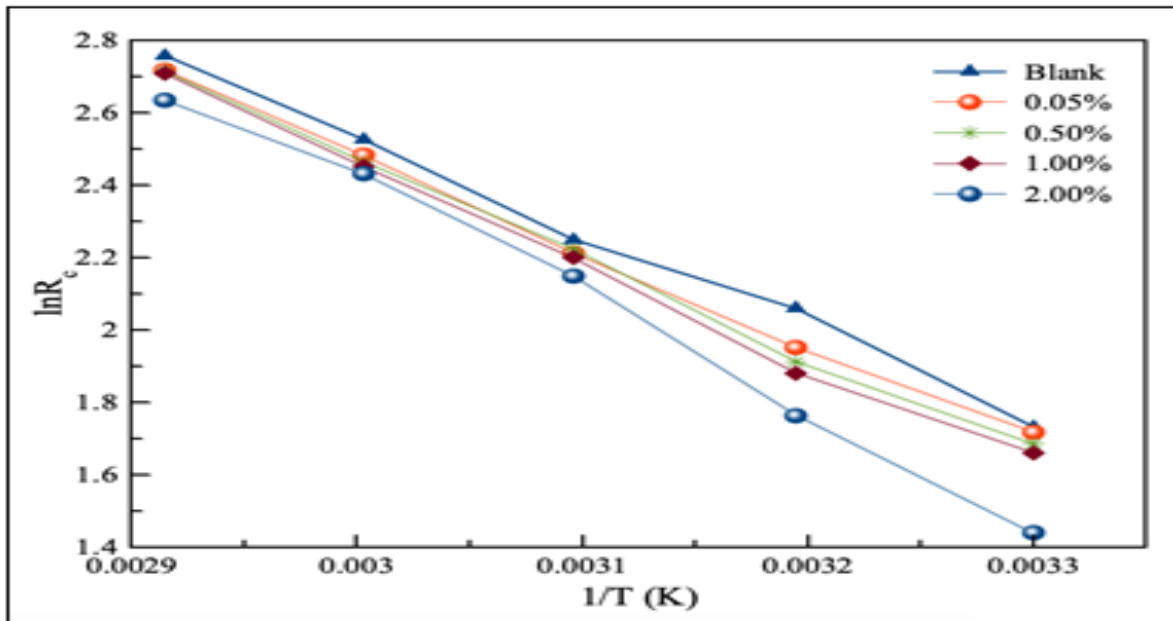


Fig. 3. Arrhenius plot for the effect of temperature.

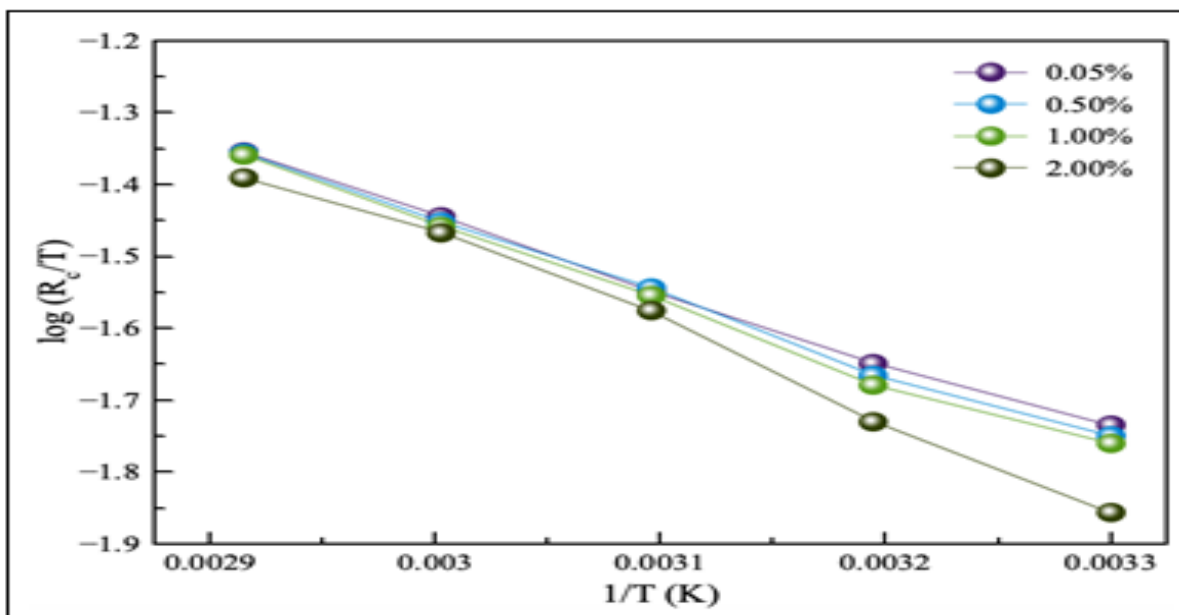


Fig. 4. Alternative Arrhenius plot for mild steel in aqueous medium in the absence and presence of different concentrations of RDF extract.

Surface examination studies

The specimens were also studied under an optical microscope with two light sources. The images for the different set-ups are shown in Fig. 6.

Fig. 6A shows an image of the corroded surface of the metal sample from the treatment containing 0.05% dragon fruit extract. The micrograph of the representative metal samples from the other three treatments, specifically the treatments containing

0.50%, 1.00%, and 2.00% dragon fruit extract, are also depicted in Fig.6 B-D. In addition, micrographs were also taken for the surface examination studies of the negative and positive control (WD-40) set-ups, as shown in Fig. 6E-F.

The pictures obtained from optical microscopy showed the amount of corrosion for each of the set-ups. The brownish-orange streaks in the pictures show the deposits of hydrated iron (II) oxide.

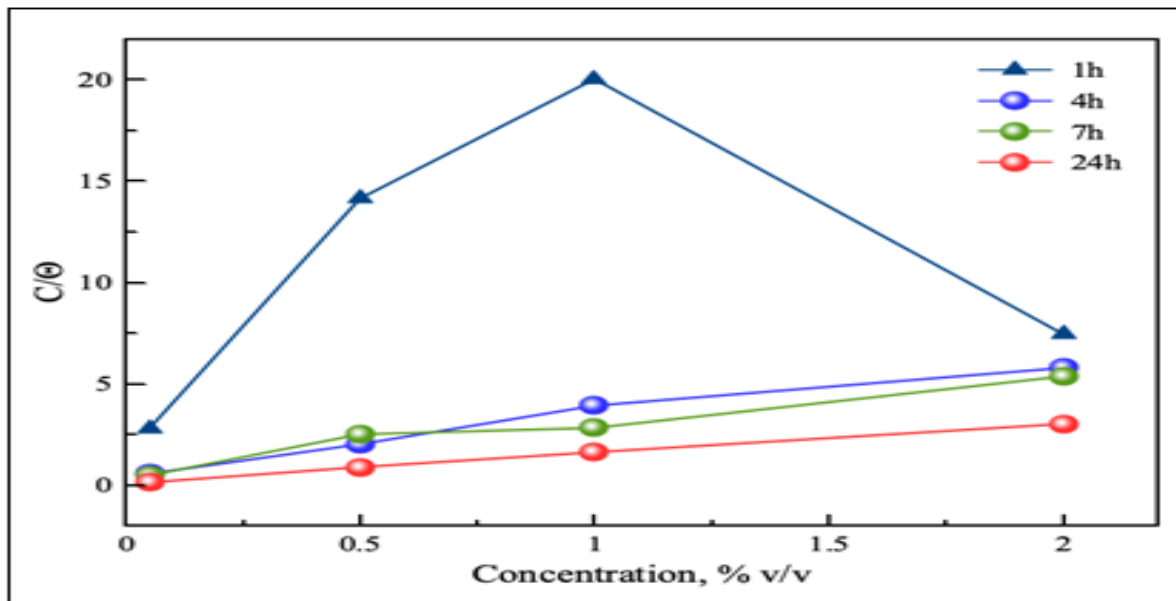


Fig. 5. Langmuir isotherm plots of MS in 1 M HCl at different concentrations of inhibitors.

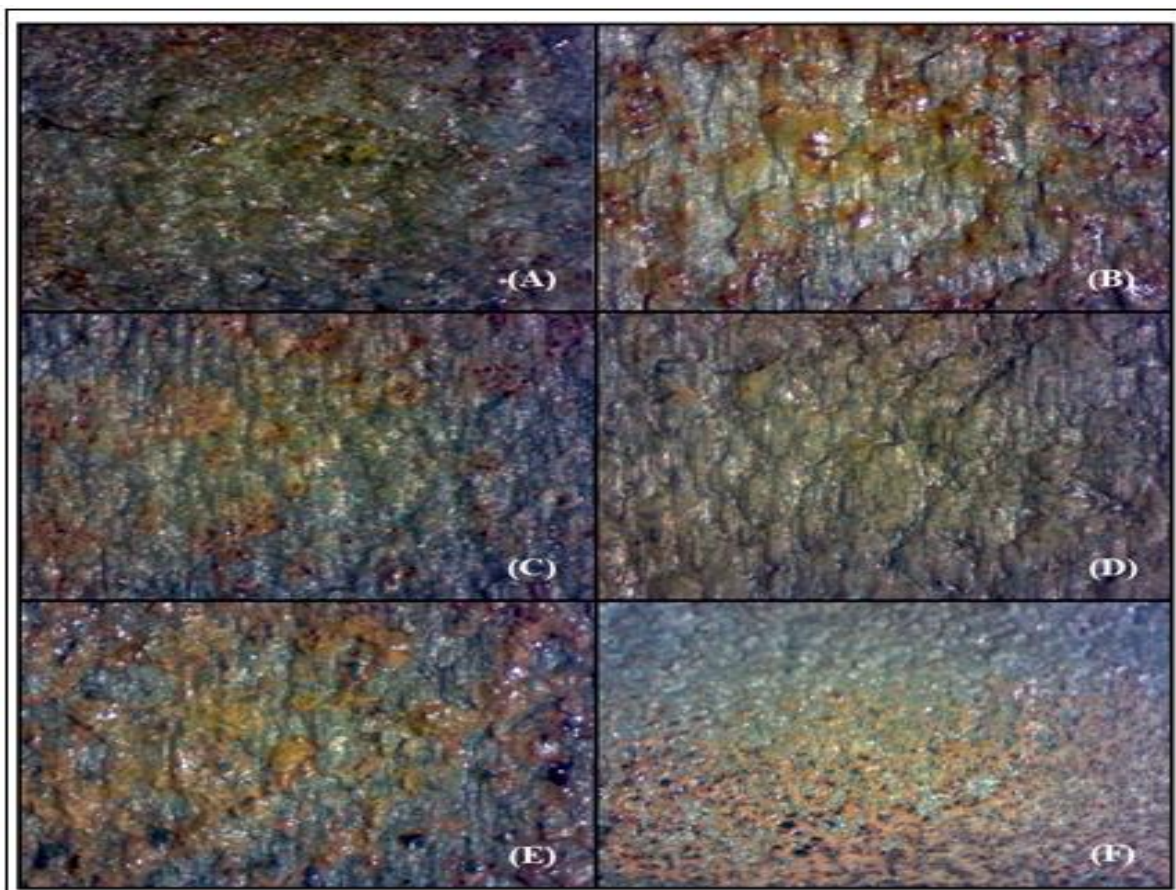


Fig. 6. Optical micrographs for uninhibited and inhibited mild steel soaked in 1M HCl.

The microscopy also revealed that the type of corrosion that occurred is pitting corrosion. Moreover, it confirms that the increase in the amount of RDF extract reduces a significant amount of corrosion that can happen on the surface of mild steel

since the amount of brownish-orange streaks decreased visibly. Furthermore, negative control, comprised of HCl only, showed the most corrosion and contained more pits on the surface.

Mechanism of inhibition

RDF extracts were previously reported to be phytochemicals with high antioxidant activities such as anthocyanins, polyphenols, and flavonoids.

Common motifs to these phytochemicals are chromophores and the presence of oxygen-heteroatom in the ring structures, which ramps up their adsorptive ability on mild steel surfaces (Fig. 7).

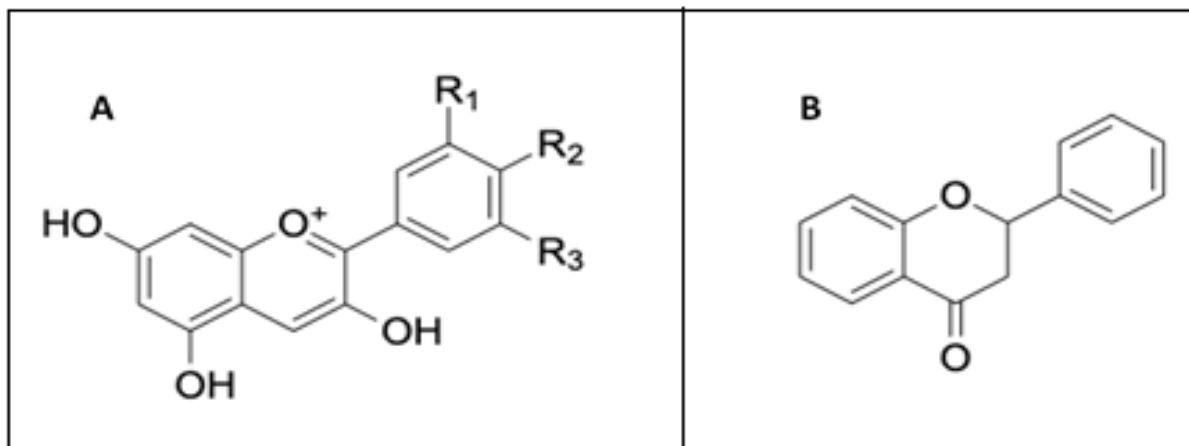


Fig. 7. General structures for (A) anthocyanins and (B) flavonoids.

The pi-electrons and lone pairs from the RDF constituents effectively associate with the unfilled d-orbital of iron and hence, serve as sites of adsorption. As seen from the thermodynamic values obtained in the present study, these organic molecule components are adsorbed physically, forming a protective envelope and thus explains their inhibitory activity against corrosion brought about by aggressive electrolytes.

Conclusion

Corrosion inhibition of RDF on mild steel exposed in an acidic medium was examined in the present study. The inhibition efficiency increases with RDF concentration and immersion time with maximum efficiency of 97% reached for 2.00% waste peel extract in 24h. Corrosion rate declined with increased RDF concentration but increased with temperature. The activation energy for the corrosion process increases with concentration due to the physisorption of RDF onto the metal surface. The adsorption process was found spontaneous and obeyed the Langmuir isotherm model. Surface examination of the specimens reveals pitting corrosion in uninhibited samples, while inhibited specimens showed little signs of oxidation. Overall, the results confirm the effectiveness of RDF as a corrosion inhibitor.

References

- Africa S.** 2008. Adsorption and inhibitive properties of ethanol extracts of *Musa sapientum* peels as a green corrosion inhibitor for mild steel in H₂SO₄. *African Journal of Pure Applied Chemistry* **2(6)**, 046-54.
<https://doi.org/10.5897/AJPAC.9000008>
- Akinbulumo OA, Odejebi OJ, Odekanle EL.** 2020. Thermodynamics and adsorption study of the corrosion inhibition of mild steel by *Euphorbia heterophylla* L. extract in 1.5 M HCl. *Results in Materials* **5**, 100074.
<https://doi.org/10.1016/j.rinma.2020.100074>
- Al-Amiery A, Salman TA, Alazawi KF, Shaker LM, Kadhum AA, Takriff MS.** 2020. Quantum chemical elucidation on corrosion inhibition efficiency of Schiff base: DFT investigations supported by weight loss and SEM techniques. *International Journal of Low-Carbon Technology* **15(2)**, 202-9.
<https://doi.org/10.1093/ijlct/ctz074>
- Al Maofaria A, Doucha S, Benmessaouda M, Hajjaji SE, Mosaddak M, Ouaki B.** 2021. Inhibition Study of Various Extracts of *Tribulus*

Terrestris Plant on the Corrosion of Mild Steel in a 1.0 M HCl Solution. *Portugaliae Electrochimica Acta* **39(1)**, 21-35.

<https://doi.org/10.4152/pea.202101021>

Bayol E, Gürten AA, Dursun M, Kayakirilmaz K. 2008. Adsorption behavior and inhibition corrosion effect of sodium carboxymethyl cellulose on mild steel in acidic medium. *Acta Physico-Chimica Sinica* **24(12)**, 2236-43.

[https://doi.org/10.1016/S1872-1508\(08\)60085-6](https://doi.org/10.1016/S1872-1508(08)60085-6)

Dehghani A, Bahlakeh G, Ramezanzadeh B, Ramezanzadeh M. 2020. Potential role of a novel green eco-friendly inhibitor in corrosion inhibition of mild steel in HCl solution: Detailed macro/micro-scale experimental and computational explorations. *Construction and Building Materials* **245**, 118464.

<https://doi.org/10.1016/j.conbuildmat.2020.118464>

El Hamdani N, Fdil R, Tourabi M, Jama C, Bentiss F. 2015. Alkaloids extract of *Retama monosperma* (L.) Boiss. seeds used as novel eco-friendly inhibitor for carbon steel corrosion in 1 M HCl solution: Electrochemical and surface studies. *Applied Surface Science* **357**, 1294-305.

<https://doi.org/10.1016/j.apsusc.2015.09.159>

Graham D. 1953. The characterization of physical adsorption systems. I. The equilibrium function and standard free energy of adsorption. *Journal of Physical Chemistry* **57(7)**, 665-669.

<https://doi.org/10.1021/j150508a014>

Hajjaji FE, Salim R, Taleb M, Benhiba F, Rezki N, Chauhan DS, Quraishi MA. 2021. Pyridinium-based ionic liquids as novel eco-friendly corrosion inhibitors for mild steel in molar hydrochloric acid: Experimental & computational approach. *Surfaces & Interfaces* **22**, 100881.

<https://doi.org/10.1016/j.surfin.2020.100881>

Haque J, Verma C, Srivastava V, Nik WW. 2021. Corrosion inhibition of mild steel in 1M HCl using environmentally benign *Thevetia peruviana*

flower extracts. *Sustainable Chemistry and Pharmacy* **19**, 100354.

<https://doi.org/10.1016/j.scp.2020.100354>

Jyothi S, Rao YS, Ratnakumar PS. 2019. Natural product as corrosion inhibitors in various corrosive media: a review. *Rasayan Journal of Chemistry* **12(2)**, 537-44.

<https://dx.doi.org/10.31788/RJC.2019.1225000>

Kavitha N, Kathiravan S, Jyothi S, Muruges A, Ravichandran J. 2019. Adsorption and inhibitive properties of methanol extract of *Leucas aspera* leaves for the corrosion of mild steel in HCl medium. *Journal of Bio-and Tribo-Corrosion* **5(2)**, 1-1.

<https://doi.org/10.1007/s40735-019-0244-6>

Krishnaveni K, Ravichandran J. 2014. Effect of aqueous extract of leaves of *Morinda tinctoria* on corrosion inhibition of aluminium surface in HCl medium. *Transaction of Nonferrous Metal Society of China* **24(8)**, 2704-12.

[https://doi.org/10.1016/S1003-6326\(14\)63401-4](https://doi.org/10.1016/S1003-6326(14)63401-4)

Li X, Deng S, Fu H. 2011. Inhibition by tetradecylpyridinium bromide of the corrosion of aluminium in hydrochloric acid solution. *Corrosion Science* **53(4)**, 1529-36.

<https://doi.org/10.1016/j.corsci.2011.01.032>

Nahlé A, Salim R, El Hajjaji F, Aouad MR, Messali M, Ech-Chihbi E, Hammouti B, Taleb M. 2021. Novel triazole derivatives as ecological corrosion inhibitors for mild steel in 1.0 M HCl: experimental & theoretical approach. *RSC Advances* **11(7)**, 4147-62.

<https://doi.org/10.1039/D0RA09679B>

Ogunleye OO, Arinkoola AO, Eletta OA, Agbede OO, Osho YA, Morakinyo AF, Hamed JO. 2020. Green corrosion inhibition and adsorption characteristics of *Luffa cylindrica* leaf extract on mild steel in hydrochloric acid environment. *Heliyon*. **6(1)**, e03205.

<https://doi.org/10.1016/j.heliyon.2020.e03205>

Paul PK, Yadav M, Obot IB. 2021. Potential of dibenzo-18-crown-6-ether derivatives as a corrosion inhibitor on mild steel in HCl medium: electrochemical and computational approaches. *New Journal of Chemistry* **45(15)**, 6826-42.

<https://doi.org/10.1039/D1NJ00869B>

Padmavathy K, Sivakumari K, Karthika S, Rajesh S, Ashok K. 2021. Phytochemical profiling and anticancer activity of dragon fruit *Hylocereus undatus* extracts against human hepatocellular carcinoma cancer (hepg-2) cells. *International Journal of Pharmaceutical Science & Research* **12(5)**, 2770-78.

[https://doi.org/10.13040/IJPSR.0975-8232.12\(5\).2770-78](https://doi.org/10.13040/IJPSR.0975-8232.12(5).2770-78)

Prabakaran M, Kim SH, Kalaiselvi K, Hemapriya V, Chung IM. 2016. Highly efficient *Ligularia fischeri* green extract for the protection against corrosion of mild steel in acidic medium: electrochemical and spectroscopic investigations. *Journal of Taiwan Institute of Chemical Engineering* **59**, 553-62.

<https://doi.org/10.1016/j.jtice.2015.08.023>

Prasad AR, Kunyankandy A, Joseph A. 2020. Corrosion Inhibition in Oil and Gas Industry. In *Corrosion Inhibitors in the Oil and Gas Industry*; V.S.

Saji and S.A. Umoren. Wiley-VCH Verlag GmbH & Co. KGaA, Weinheim, Germany 135-50.

<https://doi.org/10.1002/9783527822140.ch5>

Rosiana NM, Suryana AL, Olivia Z. 2021. Polyphenol content and antioxidant activity of beverage from dragon fruit peel powder and soy powder. *IOP Conference Series: Earth and Environmental Science* **672(1)**, 012055.

<https://doi.org/10.1088/1755-1315/672/1/012055>

Rosli NR, Yusuf SM, Sauki A, Razali WM. 2019. *Musa sapientum* (Banana) peels as green corrosion inhibitor for mild steel. In *Key Engineering Materials*. Trans Tech Publications Ltd. Freienbach, Switzerland **797**, p 230-239.

<https://doi.org/10.4028/www.scientific.net/KEM.797.230>

Sedik A, Lerari D, Salci A, Athmani S, Bachari K, Gecibesler IH, Solmaz R. 2020. Dardagan Fruit extract as eco-friendly corrosion inhibitor for mild steel in 1 M HCl: Electrochemical and surface morphological studies. *Journal of Taiwan Institute of Chemical Engineering* **107**, 189-200.

<https://doi.org/10.1016/j.jtice.2019.12.006>

Telegdi J. 2020. Formation of Self-Assembled Anticorrosion Films on Different Metals. *Materials* **13(22)**, 5089.

<https://doi.org/10.3390/ma13225089>